

Conference materials

UDC 535.372

DOI: <https://doi.org/10.18721/JPM.183.104>

Hybrid emitters based on two-dimensional WSe₂ and ordered plasmonic nanobumps

A.V. Nikolaeva^{1, 2} ✉, M.A. Anikina^{1, 2}, V.M. Kondratev^{1, 2},
V.A. Sharov^{1, 3}, E.Yu. Barulina⁴, V.O. Gridchin^{5, 1, 6},
A.I. Khrebtov⁶, A.A. Kuchmizhak⁵, A.D. Bolshakov^{1, 2, 6, 7}

¹ Alferov University, St. Petersburg, Russia;

² Moscow Institute of Physics and Technology, Moscow, Russia;

³ Ioffe Institute, St. Petersburg, Russia;

⁴ Russian Quantum Center, Moscow, Russia;

⁵ Institute for Analytical Instrumentation of the RAS, St. Petersburg, Russia;

⁶ St. Petersburg State University, St. Petersburg, Russia;

⁷ Far Eastern Federal University, Vladivostok, Russia;

⁸ Yerevan State University, Yerevan, Armenia

✉ nikalex2000@bk.ru

Abstract. Two-dimensional transition metal dichalcogenides (TMDs), particularly tungsten diselenide (WSe₂), exhibit exceptional optoelectronic properties, including strong light-matter interactions and tunable exciton behavior, making them promising for nanophotonic applications. This work investigates a hybrid system comprising a WSe₂ monolayer integrated with a plasmonic metasurface of Au-nanobumps to enhance photoluminescence (PL) through exciton-plasmon coupling and strain-induced bandgap modulation. The WSe₂ monolayers were mechanically exfoliated and transferred onto a laser-patterned Au-nanobump array fabricated via femtosecond laser printing, offering a scalable alternative to conventional lithography. Optical characterization showed a threefold enhancement of photoluminescence intensity of WSe₂ monolayer lying on a nanobump compared to WSe₂ on a flat gold substrate, what attributed to localized plasmon-exciton interactions and strain effects. The study demonstrates a cost-effective, lithography-free approach for tailoring hybrid TMD-plasmonic systems, enabling precise control over optical properties for next-generation optoelectronic devices.

Keywords: WSe₂, emitter, nanobump, photoluminescence

Funding: The Ministry of Science and Higher Education of the Russian Federation (Grant FSRM-2023-0009; project FSMG-2025-0005; FSRM 2023-0007 project). Russian Science Foundation (Grant 24-12-00225, Grant 24-19-00541). St.-Petersburg State University research project No. 129360164.

Citation: Nikolaeva A.V., Anikina M.A., Kondratev V.M., Sharov V.A., Barulina E.Yu., Gridchin V.O., Khrebtov A.I., Kuchmizhak A.A., Bolshakov A.D., Hybrid emitters based on two-dimensional WSe₂ and ordered plasmonic nanobumps, St. Petersburg State Polytechnical University Journal. Physics and Mathematics. 18 (3.1) (2025) 30–35. DOI: <https://doi.org/10.18721/JPM.183.104>

This is an open access article under the CC BY-NC 4.0 license (<https://creativecommons.org/licenses/by-nc/4.0/>)



Материалы конференции

УДК 535.372

DOI: <https://doi.org/10.18721/JPM.183.104>

Гибридные эмиттеры на основе двумерного WSe_2 и упорядоченных плазмонных нанобампов

А.В. Николаева^{1, 2} ✉, М.А. Аникина^{1, 2}, В.М. Кондратьев^{1, 2},

В.А. Шаров^{1, 3}, Е.Ю. Барулина⁴, В.О. Гридчин^{5, 1, 6},

А.И. Хребтов⁶, А.А. Кучмижак⁷, А.Д. Большаков^{1, 2, 8}

¹ Академический университет им. Ж.И. Алфёрова РАН, Санкт-Петербург, Россия;

² Московский физико-технический институт (национальный исследовательский университет), г. Долгопрудный, Россия;

³ Физико-технический институт им. А.Ф. Иоффе РАН, Санкт-Петербург, Россия;

⁴ Российский квантовый центр, Москва, Россия;

⁵ Институт аналитического приборостроения РАН, Санкт-Петербург, Россия;

⁶ Санкт-Петербургский государственный университет, Санкт-Петербург, Россия;

⁷ Дальневосточный федеральный университет, г. Владивосток, Россия;

⁸ Ереванский государственный университет, г. Ереван, Армения

✉ nikalex2000@bk.ru

Аннотация. Двумерные дихалькогениды переходных металлов (TMDs) широко известны благодаря своим уникальным оптическим и электрическим свойствам, в особенности двумерный WSe_2 обладает выдающимися люминесцентными характеристиками, что делает его перспективным кандидатом для применений в нанофотонике. В данной работе исследуется гибридная система, состоящая из монослоя WSe_2 , интегрированного с плазмонной поверхностью упорядоченных Au-нанобампов, изготовленных с помощью метода фемтосекундной лазерной печати, предлагающий масштабируемую альтернативу традиционным методам литографии и травления. Оптическая характеристика показала трехкратное усиление интенсивности ФЛ монослоя WSe_2 на нанобампе по сравнению с WSe_2 , лежащим на плоской золотой подложке, что можно объяснить локализованным плазмон-экситонным взаимодействием и деформационными эффектами. Исследование демонстрирует экономически эффективный подход к созданию гибридных TMDs-плазмонных систем, позволяющий точно контролировать оптические свойства двумерного WSe_2 для применения в оптоэлектронных устройствах следующего поколения.

Ключевые слова: WSe_2 , эмиттер, фотолюминесценция

Финансирование: Министерство науки и высшего образования Российской Федерации (грант FSRM-2023-0009; проект FSMG-2025-0005; FSRM 2023-0007 проект). Российский научный фонд (грант 24-12-00225, грант 24-19-00541). СПбГУ, шифр проекта 129360164.

Ссылка при цитировании: Николаева А.В., Аникина М.А., Кондратьев В.М., Шаров В.А., Барулина Е.Ю., Гридчин В.О., Хребтов А.И., Кучмижак А.А., Большаков А.Д. Гибридные эмиттеры на основе двумерного WSe_2 и упорядоченных плазмонных нанобампов // Научно-технические ведомости СПбГПУ. Физико-математические науки. 2025. Т. 18. № 3.1. С. 30–35. DOI: <https://doi.org/10.18721/JPM.183.104>

Статья открытого доступа, распространяемая по лицензии CC BY-NC 4.0 (<https://creativecommons.org/licenses/by-nc/4.0/>)

Introduction

Two-dimensional materials, particularly transition metal dichalcogenides (TMDs) like MoS_2 , WS_2 , MoSe_2 , and WSe_2 , exhibit exceptional optical and electronic properties, including direct bandgaps in monolayer form, strong light-matter interactions, and tunable exciton behavior [1–3]. Among them, WSe_2 stands out for its superior luminescence, making it promising for optoelectronic applications. This work explores a hybrid system combining WSe_2 with plasmonic nanostructures to enhance optical properties through exciton-plasmon coupling [4]. Additionally, strain induced by transferring WSe_2 onto nanostructured surfaces modifies its bandgap and exciton transitions [5], further boosting photoluminescence efficiency.

Materials and Methods

In our work, WSe_2 monolayers were obtained using a mechanical exfoliation method and transferred to a target substrate with Au-nanobumps using a custom transfer system based on tsc2 hq graphene (HQ Graphene, Netherlands).

Figure 1 shows Au-nanobumps of different heights with periods of 3 μm , 5 μm and 10 μm .

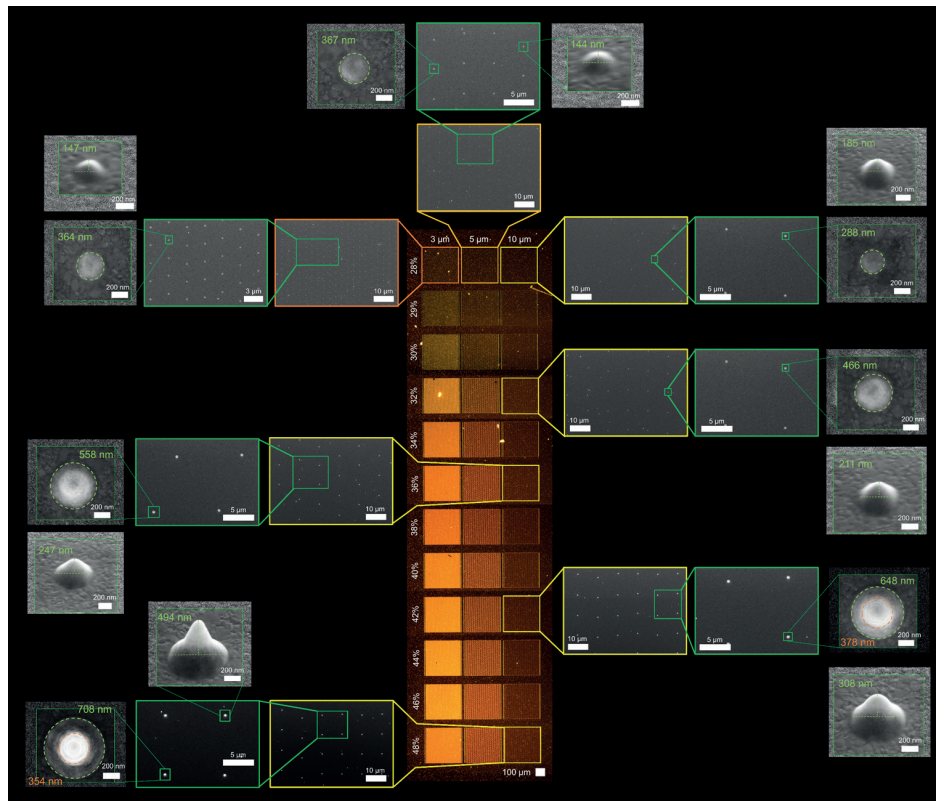


Fig. 1. Au-nanobumps: optical (center) and SEM images of nanobump arrays with periods of 3, 5 and 10 μm obtained using laser pulses of different output, expressed as a percentage, where 100% corresponds to 2 nJ

The Au-nanobumps metasurface was fabricated by combination of an inexpensive and scalable magnetron sputtering of thin Au films with a direct fs-laser printing technique. First, a gold film with a thickness of 50 nm was coated over a glass substrate using magnetron deposition. Then, laser patterning of the glass-supported Au films was carried out using ≈ 200 fs second-harmonic ($\lambda = 515$ nm) pulses generated by a regeneratively amplified Yb:KGW laser system (Pharos, Light Conversion) at 50 kHz repetition rate. Output laser radiation with a Gaussian-shaped lateral intensity profile was focused onto the Au film surface by a microscope objective (50 $\times$, Mitutoyo) with a numerical aperture $\text{NA} = 0.42$. A computer-driven nanopositioning platform (ANT130XY, Aerotech) ensured precise (position deviation less than 100 nm) movement of the sample surface with respect to the laser focal spot, allowing each pulse to form isolated nanobumps arranged into a square-shaped lattice with a period (Λ) defined by the sample scanning speed.



Results and Discussion

Optical properties of such a structure were characterized using Raman and photoluminescence (PL) microspectroscopy. The measurements were carried out on a Horiba LabRAM HR 800 spectrometer. The excitation radiation source was a diode-pumped 532 nm solid-state laser.

Figure 2, *a* presents an optical image of a WSe₂ layer transferred onto a substrate patterned with an array of Au-nanobumps (147 nm height, 364 nm base diameter), fabricated using a laser pulse output of 28% (0.56 nJ), alongside the corresponding AFM image of the same region. The WSe₂ flake exhibits two distinct zones: a monolayer (1L-WSe₂) and a bilayer (2L-WSe₂). AFM analysis reveals that the flake conforms to the nanobump topography, forming a tensile “tent”-like structure over each bump, while folding between adjacent bumps is a behavior more pronounced in the bilayer regions. Disordered Au particles of varying sizes, residual from fabrication, are also observed on the substrate. PL-mapping along two bump-to-plane directions (Fig. 2, *b*) and their spectra (Fig. 2, *c*, *d*) demonstrate two key strain-dependent effects. First, it is an enhanced PL-intensity as the monolayer approaches the bump region (higher strain), attributed to exciton localization suppressing non-radiative recombination and plasmonic nanoantenna effects from Au-nanobumps amplifying the local electromagnetic field. Second, it is a redshift of the PL-peak (by a few nm) under tensile strain, consistent with bandgap reduction in the deformed WSe₂ lattice.

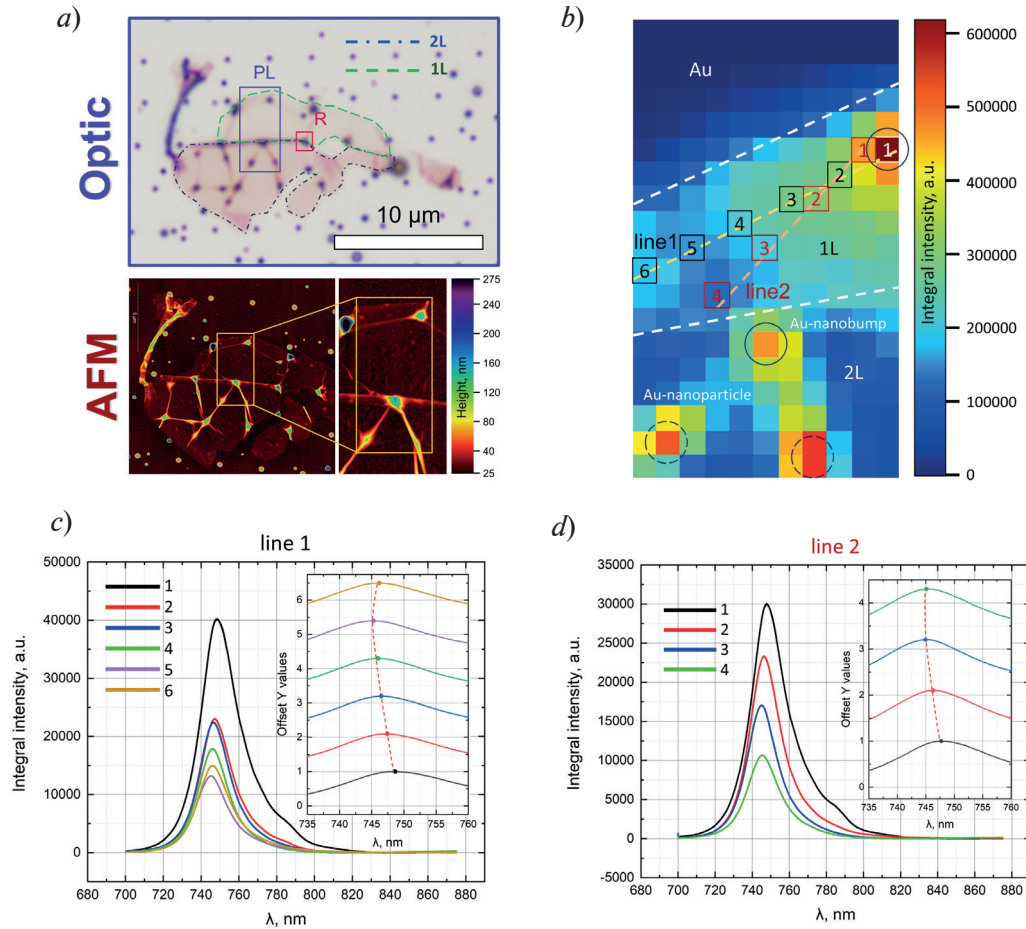


Fig. 2. WSe₂ on Au-nanobumps (28%): optical image (above) with the selected areas “PL” and “R” and AFM-image (below) (*a*); PL-mapping of the selected area “PL” representing integral intensity of a PL-spectra (*b*); PL-spectra of line 1 (*c*) and line 2 (*d*) with the addition of waterfall graph showing the shift of the PL-peak respectively (*c*)

To characterize the mono- and bilayer regions of WSe₂, Raman mapping was performed in area “R” (Fig. 2, *a*). The bilayer region exhibits significantly higher integrated Raman spectra intensity compared to the monolayer (Fig 3, *a*). The spatial boundary between 1L-WSe₂ and 2L-WSe₂

is further confirmed by the shift in the A'_1 peak position (Fig. 3, *b*), with the bilayer showing a distinct cm^{-1} -scale shift. Representative Raman spectra (Fig. 3, *c, d*) reveal key differences: the bilayer not only shows enhanced A'_1 and E' modes due to modified electron-phonon coupling but also displays new characteristic modes. The observed modes include a shear mode (ZO') at 138 cm^{-1} , arising from interlayer displacement, a layer breathing mode (LBM) at 311 cm^{-1} , indicative of strong interlayer interactions and also new optical modes at 376 cm^{-1} and 397 cm^{-1} , activated by the reduced crystal symmetry in the bilayer.

Notably, complete photoluminescence quenching was absent at the WSe_2/Au interface, suggesting high quantum efficiency in the WSe_2 monolayer. The enhanced PL intensity in this system likely stems from two synergistic effects: strain-induced modification of the WSe_2 monolayer and plasmonic enhancement from the Au-nanobumps.

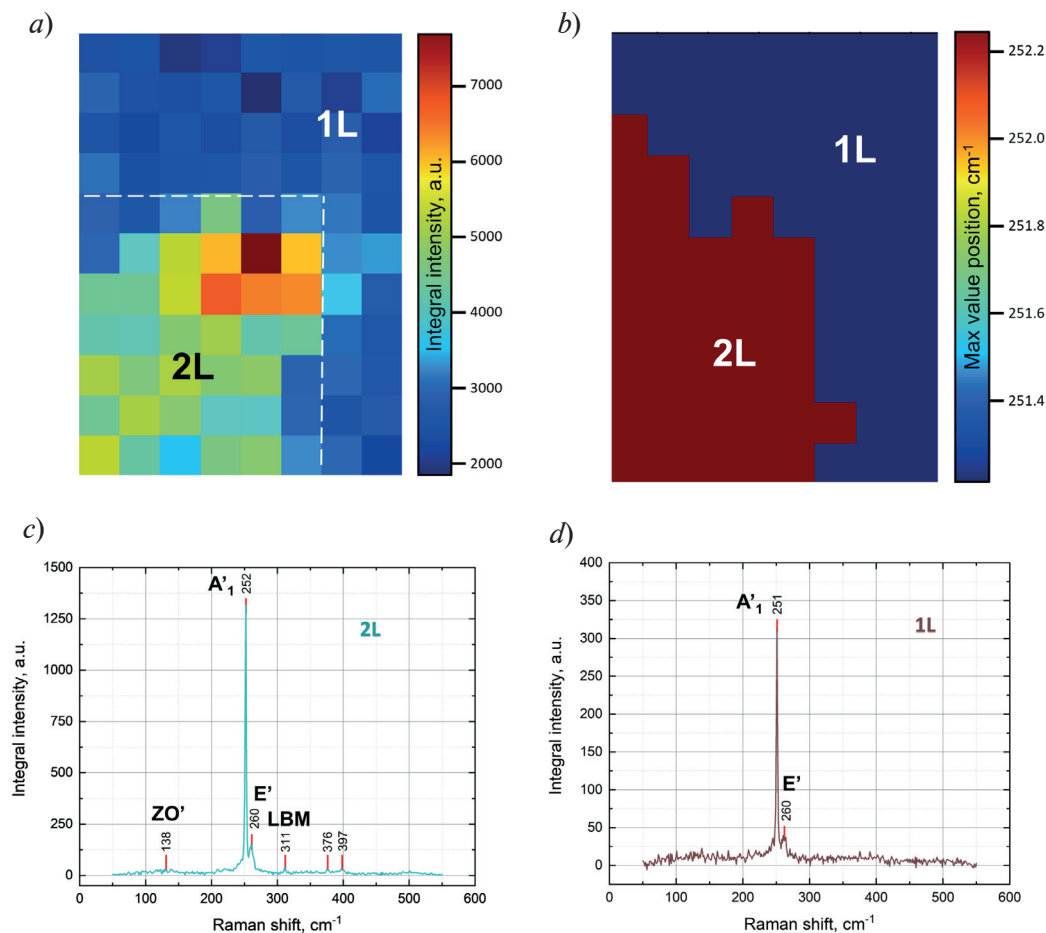


Fig. 3. WSe_2 on Au-nanobumps (28%): Raman mapping of the area R representing integral intensity (*a*) and the primary peak position in cm^{-1} (*b*) of Raman spectra; 2L- WSe_2 (*c*) and 1L- WSe_2 (*d*) Raman spectra with the designation of the main modes of combined light scattering

Conclusion

The innovation and practical significance of the presented work is attributed to the use of Au-nanobumps, the formation of which is carried out by a simple and effective method alternative to the traditional processes of lithography and etching. The laser radiation parameters allow controlling the geometry of the nanobumps and the lattice period, which provides the possibility of precise control over the optical characteristics of the hybrid structure. Furthermore, the ability to transfer two-dimensional WSe_2 layers onto such structures with good adhesion provides an avenue for the fabrication of efficient hybrid emitters and heterostructures based on this platform.



Acknowledgments

A.D.B. acknowledges Russian Science Foundation (Grant 24-12-00225) for support of the experiments. A.V.N. thanks The Ministry of Science and Higher Education of the Russian Federation (Grant FSRM-2023-0009) for support of analysis of the experimental data. M.A.A. thanks The Ministry of Science and Higher Education of the Russian Federation (project FSMG-2025-0005) for support of Raman and photoluminescence microspectroscopy analysis. V.A.S. thanks the Ministry of Science and Higher Education of the Russian Federation (FSRM 2023-0007 project) for the financial support of AFM measurements. A.A.K. acknowledges Russian Science Foundation (Grant 24-19-00541) for support of sample fabrication. A.I.K. acknowledges support of the manuscript preparation St.-Petersburg State University for a research project No. 129360164.

REFERENCES

1. Kuznetsov A., Anikina M.A., Toksumakov A.N., Abramov A.N., Dremov V.V., Zavyalova E., Kondratev V.M., Fedorov V.V., Mukhin I.S., Kravtsov V., Novoselov K.S., Arsenin A.V., Volkov V.S., Ghazaryan D.A., Bolshakov A.D., In-Plane Directional MoS₂ Emitter Employing Dielectric Nanowire Cavity, *Small Struct* (2025).
2. Ermolaev G.A., Stebunov Y.V., Vyshnevyy A.A., Tatarkin D.E., Yakubovsky D.I., Novikov S.M., Baranov D.G., Shegai T., Nikitin A.Y., Arsenin A.V., Volkov V.S., Broadband optical properties of monolayer and bulk MoS₂, *NPJ 2D Mater Appl.* 4 (2020) 21.
3. Splendiani A., Sun L., Zhang Y., Li T., Kim J., Chim C.-Y., Galli G., Wang F., Emerging Photoluminescence in Monolayer MoS₂, *Nano Lett.* 10 (2010) 1271–1275.
4. Mueller N.S., Arul R., Kang G., Saunders A.P., Johnson A.C., Sánchez-Iglesias A., Hu S., Jakob L.A., Bar-David J., de Nijs B., Liz-Marzán L.M., Liu F., Baumberg J.J., Photoluminescence upconversion in monolayer WSe₂ activated by plasmonic cavities through resonant excitation of dark excitons, *Nat Commun.* 14 (2023) 5726.
5. Gong Y., Zhou Q., Huang X., Han B., Fu X., Gao H., Li F., Dr. Tian Cui T., Pressure-Induced Photoluminescence Adjustment and Lattice Disorder in Monolayer WSe₂, *ChemNanoMat.* 3 (2017) 238–244.

THE AUTHORS

NIKOLAEVA Aleksandra V.
nikalex2000@bk.ru
ORCID: 0009-0008-4344-4863

ANIKINA Maria A.
mari.a.nikina@yandex.ru
ORCID: 0000-0002-5522-5026

KONDRATEV Valeriy M.
kvm_96@mail.ru
ORCID: 0000-0002-3469-5897

SHAROV Vladislav A.
vl_sharov@mail.ru
ORCID: 0000-0001-9693-5748

BARULINA Elena Yu.
barulina.eu@mipt.ru
ORCID: 0000-0001-7087-0552

GRIDCHIN Vladislav O.
gridchinvo@gmail.com
ORCID: 0000-0002-6522-3673

KHREBTOV Artem I.
khrebtovart@mail.ru
ORCID: 0000-0001-5515-323X

KUCHMIZHAK Aleksandr A.
alex.iacp.dvo@mail.ru
ORCID: 0000-0002-5376-5555

BOLSHAKOV Alexey D.
acr1235@mail.ru
ORCID: 0000-0001-7223-7232

Received 08.08.2025. Approved after reviewing 28.08.2025. Accepted 24.09.2025.